

Effect of high temperature on various indirect restorations in forensic identification - An *in vitro* study

G. Lokhasudhan, P. Ajitha

Departments of Conservative Dentistry and Endodontics, Saveetha Dental College, Saveetha University, Chennai, Tamil Nadu, India

Correspondence to: P. Ajitha, Departments of Conservative Dentistry and Endodontics, Saveetha Dental College, Saveetha University, Chennai, Tamil Nadu, India.
Phone: +91-9962782824. E-mail: ajitharijesh@gmail.com

ABSTRACT

The forensic odontologist utilizes the human dentition throughout each stage of dental evaluation, and restorations are as unique as fingerprints, and their radiographic morphology, as well as the types of filling materials, are often the main feature for identification. The detection of residual restorative material and composition of unrecovered adjacent restoration is a valuable toolmark in the presumptive identification of the dentition of a burned victim. Zirconia, composite, lithium disilicate, and so on have a different resistance to prolonged high temperature. Therefore, the identification of burned bodies can be correlated with adequate qualities and quantities of the traces. Most of the odontogenic examination relies heavily on the existence of the restoration as well as the relationship of one dental structure to another. This greatly narrows the research for the final identification that is based on postmortem data. The purpose of this study is to examine the resistance of teeth and different indirect restorative materials, to variable temperature and duration, for identification. The crowns were fabricated ($n = 10$) with one of the following materials Group 1: Lithium disilicate (Emax ivoclar, vivadent), Group 2: Zirconia (BruxZir-Glidwell laboratories, USA), and Group 3: Indirect composite resin (Adoro ivoclar, vivadent). Crowns were heated in the furnace to 400°C and 1100°C during different time intervals (400°C for 5 min, 400°C for 15 min, 400°C for 30 min, and 1100°C for 15 min) and assess for surface characteristics based on visual image analysis by Patidar *et al.*, 2010. The zirconia used in this study proved to be more resistible to heat, and it proves to be the better material of choice as a forensic tool since it did not show much of a change in the morphology even at the higher temperature compared to composite and lithium disilicate.

Keywords: Composite resin matrix, lithium disilicate, zirconia

Introduction

In forensic medicine, although there is various method playing an important role in personal identification, the forensic odontology is one of the reliable methods for identifying an individual.

Fire disasters are one of the major disasters where identification of an individual is very difficult compared to other disasters. The dental remains can be observed with our naked eyes, and few minor details can be observed using microscope for better identification of the victim.

Identification of burned bodies starts with the objects that have remained with the body. Teeth are considered to be the most

indestructible components of the human body. Teeth have the superior resistance to most environmental effects such as fire, desiccation, and decomposition of the victim. Teeth survive most natural disasters and provide a positive, personal identification. It begins with the correlation of dental records to observed restorations.^[1] As the destruction of the burned victims of the third, fourth, and fifth categories is extensive, such remains cannot be identified visually and odontologists are called to assist in the identification.^[2]

In recent years, dentistry has been benefited from a marked increase in the development of esthetic materials. However, the usefulness of traditional materials has not been eliminated. Forensic odontology is concerned with the identification of different restorative materials subjected to variable temperatures, which provide important postmortem clues with the availability of premortem records.^[3] In cases of mass disasters associated with fire, identification of the burned victims can be a real challenge to the forensic team.^[4] By evaluating the previously restored teeth and fractured bone after the burn can ensure maximum data and help in identification of the burned body.

In forensic odontology, there are several things such as restorations, root canal filling that we can analyze for identification

Access this article online

Website: www.japer.in

E-ISSN: 2249-3379

How to cite this article: Lokhasudhan G, Ajitha P. Effect of high temperature on various indirect restorations in forensic identification - An *in vitro* study. J Adv Pharm Edu Res 2017;7(2):157-159.

Source of Support: Nil, **Conflict of Interest:** None declared.

of the victim. As a postendodontic restoration, we give crowns which are made of various materials available in the market. In our study, we examined the effect on different materials used for the fabrication of crowns. With this study, we would be able to find the temperature that the material could withstand at various time intervals.

Materials and Methods

The crowns were fabricated ($n = 10$) with one of the following materials

- Group 1: Lithium disilicate (Emax ivoclar, vivadent)
- Group 2: Zirconia (BruxZir-Glidwell laboratories, USA)
- Group 3: Indirect composite resin (Adoro ivoclar, vivadent).

The fabricated crowns were kept separately in three different plates. Crowns were heated in the furnace to 400°C and 1100°C during different time intervals (400°C for 5 min, 400°C for 15 min, 400°C for 30 min, and 1100°C for 15 min) and assess for surface characteristics based on visual image analysis by Patidar *et al.*, 2010.^[5] Three plates containing crowns of different groups were prepared by an investment material of approximately equal dimension and numbered as - Plate 1, Plate 2, and Plate 3: The crowns which were fabricated under each group were kept totally immersed in the investment material, with the aim of simulating the clinical scenario. When the furnace reaches the temperature to the level which we are going to analyze the crowns were kept in the furnace at various time intervals which were mentioned above.

Results

The effect of varying temperatures on the fabricated crowns was observed mainly in the form of colour change, surface characteristics, cracks and disintegration. The result of the study have been computed in the tables (Tables 1-3).

Discussion

Forensic medicine works for forensic identification. It is a multidisciplinary effort which relies on positive identification methodologies. In forensic odontology, the importance of effort goes into identifying the victim. One method of identification in forensic odontology is to examine the burned victims and their fine traces as well as to examine the resistance of teeth and restorative material that was used to high temperature.^[6]

However, there are various ways to find an individual in forensic medicine; in few mass fire disasters, the identification is being questionable. In natural fire disasters, the identification of the victim is impossible at times. In recent days, there is a great advancement in dentistry toward the restoration material. Even though there are different materials used in the field of dentistry, there are few materials which have the characteristics of having resistance toward fire. The resistance of fire depends on the physicochemical properties of the materials.^[7] There are various restorative materials showing

Table 1: Effect of different temperature and time on E-max (lithium disilicate)

Temp	Time (min)	Effect
400°C	5	No significant changes seen
400°C	15	No significant changes seen
400°C	30	Loss of glaze
1100	15	The crown melted and underwent fracture

Table 2: Effect of different temperature and time on BruxZir (Zirconia)

Temp	Time (min)	Effect
400°C	5	No significant changes seen
400°C	15	No significant changes seen
400°C	30	No significant changes seen
1100°C	15	Showed slight changes in the morphology. No major alteration noted

Table 3: Effect of different temperature and time on Adoro (indirect composite resin)

Temp	Time (min)	Effect
400°C	5	The crown shows blackish discoloration and turned to ashes
400°C	15	-
400°C	30	-
1100°	15	-

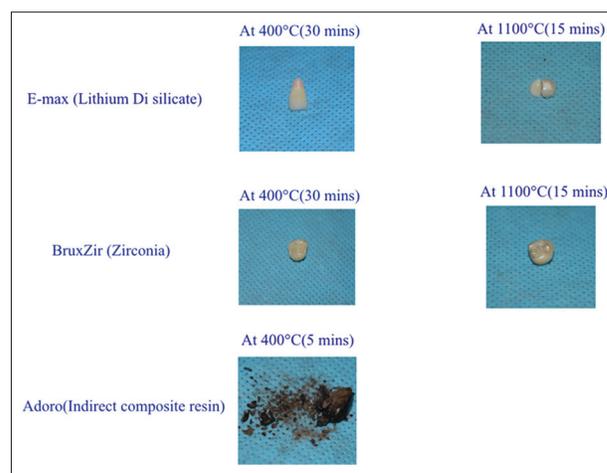


Figure 1: Visual images of indirect restorations with different time interval and at various temperatures

color changes and surface characteristics in many studies.^[3,8-10] Hence, the dental remains could be helpful for identifying an individual.

Since teeth could only be able to withstand to a particular amount of temperature, the prosthesis we use could provide better evidence to find an individual in forensic science.

In our research, the zirconia crowns (Bruxzir) could withstand higher temperature of 1100°C for 15 min with slight change in morphology (Table 2 and Figure 1) which was similarly shown by Patidar *et al.*, 2010.^[5] Which could be because of the

superior mechanical properties^[11-14] and also by the increased micromechanical properties.^[15-17] The lithium disilicate (E-max) showed loss of glaze when kept at 400°C for 30 min and the crown melted and underwent fracture at 1100°C for 15 min (Table 1 and Figure 1), whereas Adoro (indirect composite resin) crown shows blackish discoloration and turned to ashes at 400°C for 5 min (Table 3 and Figure 1).

The material was incinerated directly and not along with the tooth, surrounding tissues, and bone which might show some variations with the analysis. There could be some difference in evaluation of the material since the heat produced is artificial and not a natural heat as the temperature produced during natural disasters and fire accidents are not specific. However, this method was done to simulate the clinical scenario to an extent.

The lithium disilicate used in this study was able to withstand for an extent of heat, and then, it leads to fracture which in turn proves to be resistible when compared to the composite resin matrix which could be because of the improved characteristics^[18-20] than composite. Moreover, since the composite resin matrix is used these days conventionally for esthetic purpose which in this study, it proved to be irresistible to heat. Zirconia which was already proven to have the superior characteristics again proved to be more resistible to heat when compared to other materials used in this study. No data exist about the effects of high temperature on this material. Our findings showed that ceramic crowns did not show cracks and fragmentation at temperatures as high as 1000°C. Zirconia crown showed highest resistance to fire with no cracks and unchanged morphology, possibly due to its composition and mechanical properties of low thermal conductivity, high hardness, and chemical inertness. Even though there is several material of choice for indirect restorations, the identity of choosing the material should fulfill all the needs in a better way. Hence, zirconia as the best material of choice is used as a forensic tool and also in dentistry as a better material of choice.

By visualizing the color, cracks, and the way, it gets disintegrate will help in comparison of materials and helps to investigate in the forensic science. In future, incorporation and modification of materials in indirect restorations that withstand heat could serve as a valuable.

Conclusion

Evaluating the effect of temperature on dental prosthesis will serve as a good tool for patient identification in forensic medicine. Further studies can be done and compared with other materials of prosthesis to ensure the best material resistant to heat which can be served as the good tool for forensic investigations.

References

1. Robinson FG, Rueggeberg FA, Lockwood PE. Thermal stability of direct dental esthetic restorative materials at elevated temperatures. *J Forensic Sci* 1998;43:1163-7.
2. Ferreira JL, Espina AL, Barrios FA. The identification of victim of slaughter of the jail of Sabaneta in forensic odontology. *Rev Esp Med Leg* 1998;22:50-6.
3. Harsányi L. Scanning electron microscopic investigation of thermal damage of the teeth. *Acta Morphol Acad Sci Hung* 1975;23:271-81.
4. Bose RS, Mohan B, Lakshminarayanan L. Effects of elevated temperatures on various restorative materials: An *in vitro* study. *Indian J Dent Res* 2005;16:56-60.
5. Patidar KA, Parwani R, Wanjari S. Effects of high temperature on different restorations in forensic identification: Dental samples and mandible. *J Forensic Dent Sci* 2010;2:37-43.
6. Rotzsch K, Grundma C, Benthau S. The effect of high temperatures on human teeth and dentures. *Int Poster J Dent Oral Med* 2004;6:1-4.
7. Bagdey SP, Moharil RB, Dive AM, Thakur S, Bodhade A, Dhobley AA. Effect of various temperatures on restored and unrestored teeth: A forensic study. *J Forensic Dent Sci* 2014;6:62-6.
8. Merlati G, Savio C, Danesino P, Fassina G, Menghini P. Further study of restored and unrestored teeth subjected to high temperatures. *J Forensic Odontostomatol* 2004;22:17-24.
9. Mazza A, Merlati G, Savio C, Fassina G, Menghini P, Danesino P. Observations on dental structures when placed in contact with acids: Experimental studies to aid identification processes. *J Forensic Sci* 2005;50:406-10.
10. Muller M, Berytrand MF, Quatrehomme G, Bolla M, Rocca JP. Macroscopic and microscopic aspects of incinerated teeth. *J Forensic Odontostomatol* 1998;16:1-7.
11. Piconi C, Maccauro G. Zirconia as a ceramic biomaterial. *Biomaterials* 1999;20:1-25.
12. Cales B, Stefani Y. Mechanical properties and surface analysis of retrieved zirconia femoral hip joint heads after an implantation time of two to three years. *J Mater Sci Mater Med* 1994;5:376-80.
13. Swab JJ. Low temperature degradation of Y-TZP materials. *J Mater Sci* 1991;26:6706-14.
14. Luthardt RG, Holzhueter M, Sandkuhl O, Herold V, Schnapp JD, Kuhlisch E, *et al.* Reliability and properties of ground Y-TZP-zirconia ceramics. *J Dent Res* 2002;81:487-91.
15. Wachtman JB, Cannon WR, Matthewson MJ. *Mechanical Properties of Ceramics*. Hoboken, NJ: John Wiley and Sons; 2009. p. 228.
16. Porter DL, Evans AG, Heuer AH. Transformation-toughening in partially-stabilized zirconia (PSZ). *Acta Metallurgica* 1979;27:1649-54.
17. Evans AG, Cannon RM. Overview No. 48: Toughening of brittle solids by martensitic transformations. *Acta Metallurgica* 1986;34:761-800.
18. Mirsaneh M, Reaney IM, Hatton PV, James PF. Characterization of high-fracture toughness K-fluorrichterite-fluorapatite glass ceramics. *J Am Ceram Soc* 2004;87:240-6.
19. Mencik J. *Strength and Fracture of Glass and Ceramics*. Amsterdam, Netherlands: Elsevier; 1992.
20. Green DJ. *An Introduction to the Mechanical Properties of Ceramics*. Cambridge, UK: Cambridge University Press; 1998.

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.